

11/11/2001 16:06 6265744876

- INTRODUCTION TO CERAMICS, SECOND EDITION
W. D. Kingery, H. K. Bowen, and D. R. Uhlmann
- ANALYSIS OF METALLURGICAL FAILURES
V. J. Colangelo and F. A. Heiler
- THERMODYNAMICS OF SOLIDS, SECOND EDITION
Richard A. Swalin
- GLASS SCIENCE
Robert H. Doremus
- STEEL SUPERALLOYS
Charles T. Sims and William C. Hagel, editors
- X-RAY DIFFRACTION METHODS IN POLYMER SCIENCE
L. E. Alexander
- PHYSICAL PROPERTIES OF MOLECULAR CRYSTALS, LIQUIDS, AND GLASSES
A. Bondi
- STRUCTURE OF STRUCTURAL MATERIALS
A. S. Treiman and A. J. McBratney, Jr.
- ORGANIC SEMICONDUCTORS
F. Guimaraes and L. E. Lyons
- INTERMETALLIC COMPOUNDS
J. H. Westbrook, editor
- THE PHYSICAL PRINCIPLES OF MAGNETISM
Allen H. Morrish
- PHYSICS OF MAGNETISM
Seirin Chikazumi
- PHYSICS OF III-V COMPOUNDS
Offield Modeling (translation by D. Meyerhofer)
- PRINCIPLES OF SOLIDIFICATION
Bruce Chalmers
- MECHANICAL PROPERTIES OF MATTER
A. H. Cottrell
- THE ART AND SCIENCE OF GROWING CRYSTALS
J. J. Gilman, editor
- SELECTED VALUES OF THERMODYNAMIC PROPERTIES OF METALS AND ALLOYS
Ralph Hultgren, Raymond L. Ott, Philip D. Anderson and Kenneth K. Kelly
- MECHANISMS OF CREEP AND FATIGUE IN METALS
A. J. Kennedy
- TUNGSTEN AND TANTALUM
Frank T. Stice and Edward Eyring, editors
- TRANSMISSION ELECTRON MICROSCOPY OF METALS
Gareth Thomas
- PLASTICITY AND CREEP OF METALS
J. D. Lubahn and R. P. Fiedler
- PHYSICAL METALLURGY
Bruce Chalmers
- THE MELTING, SECOND EDITION
William G. Pryan

EXHIBIT C

Introduction to Ceramics Second Edition

W. D. Kingery

PROFESSOR OF CERAMICS
 MASSACHUSETTS INSTITUTE OF TECHNOLOGY

H. K. Bowen

ASSOCIATE PROFESSOR OF CERAMICS
 MASSACHUSETTS INSTITUTE OF TECHNOLOGY

D. R. Uhlmann

PROFESSOR OF CERAMICS AND POLYMERS
 MASSACHUSETTS INSTITUTE OF TECHNOLOGY

A Wiley-Interscience Publication

JOHN WILEY & SONS

New York • Chichester • Brisbane • Toronto • Singapore

11/10/2001, 16:06 6265744876

R&D ADMINISTRATION

#3866 P.007

Copyright © 1960, 1976 by John Wiley & Sons, Inc.

All rights reserved. Published simultaneously in Canada.

Reproduction or translation of any part of this work beyond that permitted by Sections 107 or 108 of the 1976 United States Copyright Act without the permission of the copyright owner is unlawful. Requests for permission or further information should be addressed to the Permissions Department, John Wiley & Sons, Inc.

Library of Congress Cataloging in Publication Data:

Kingery, W. D.

Introduction to ceramics.

(Wiley series on the science and technology of materials)

"A Wiley-Interscience publication."

Includes bibliographical references and index.

I. Ceramics. I. Bowen, Harvey Kent, joint author.
II. Uhlmann, Donald Robert, joint author. III. Title.

TP807.K52 1975 666 73-22248

ISBN 0-471-47860-1

Printed in the United States of America

35 14

Preface to the Second Edition

During the fifteen years which have passed since the first edition was published, the approach described has been widely accepted and practiced. However, the advances made in understanding and controlling and developing new ceramic processes and products have required substantial modifications in the text and the introduction of a considerable amount of new material.

In particular, new and deeper understanding of the structure of noncrystalline solids and the characteristics of structural imperfections, new insight into the nature of surfaces and interfaces, recognition of spinodal decomposition as a viable alternative to classical nucleation, recognition of the widespread occurrence of phase separation, development of glass-ceramics, clearer understanding of some of the nuances of sintering phenomena, development of scanning electron microscope and transmission electron microscope techniques for the observation of microstructure, a better understanding of fracture and thermal stresses and a myriad of developments relative to electrical, dielectric, and magnetic ceramics have been included. The breadth and importance of these advances has made a single author text beyond any individual competence.

The necessary expansion of material related to physical ceramics, and the recent availability of excellent texts aimed at processing and manufacturing methods [F. N. Norton, *Fine Ceramics*, McGraw-Hill, New York (1970); F. H. Norton, *Refractories*, McGraw-Hill, New York (1961); F. I. Norton, *Elements of Ceramics*, second ed., Addison Wesley Publ. Co. (1974); F. V. Tooley, ed., *Handbook of Glass Manufacture*, 2 Vols. Oxyden Publ. Co. (1961); A. Davidson, ed., *Handbook of Preceramic*

different from that of the matrix is the most satisfactory; sodium and calcium fluoride are very commonly used, as indicated in Table 13.5.

Frequently the translucency of single-phase oxide ceramics is cited as an indication of their overall quality. This index of quality works reasonably well because the pore size is similar in different bodies and the translucency depends almost exclusively on the pore concentration. (Strength and other properties are closely related to the porosity.) In aluminum oxide, for example, the index of refraction of the solid is relatively high ($n_D = 1.8$), whereas the index of refraction of the pore phase is near unity, giving a relative index of 1.8, which is very high. The pore size for these bodies usually corresponds to the original particle size of the starting material (frequently 0.5 to 2 microns) and is nearly the wavelength of the incident radiation so that the scattering is a maximum. Consequently, as indicated in Fig. 13.18, the transmission is found to be reduced to 0.01% by the addition of about 3% porosity. Even when the porosity is reduced to a value of 0.3%, the transmission is still only about 10% that of a completely dense sample. That is, for high-density single-phase ceramics containing fine porosity the translucency is a sensitive measure of the residual porosity and consequently a good indication of the quality of the ware.

The aesthetic value of many porcelain compositions is judged by the translucency. This together with good mechanical properties is the basis for compositions such as bone china and hard porcelain having high translucency. For porcelain bodies the phases present are normally a glass having an index of refraction of approximately 1.5, mullite ($n_D = 1.64$), and quartz ($n_D = 1.55$). As discussed in Chapter 11, in the normal microstructure of dense vitrified porcelain the mullite phase appears as fine needle crystals in a glassy matrix with larger quartz crystals which are undissolved or partially dissolved (see Fig. 11.11). Consequently, although the particle size of the mullite is in the micron range, the particle size and because of the greater difference in the index of refraction, the mullite phase is the main contributor to scattering and decreased translucency in porcelain bodies. The primary method by which the translucency can be increased is to increase the glass content, decreasing the amount of mullite present. This can be accomplished, for example, by increasing the ratio of feldspar to clay, as discussed in Chapters 7 and 11. Frit porcelains and compositions, such as dental porcelains having a high feldspar content, are given high translucency by increasing the amount of glass at the expense of mullite development. For other purposes, however, this is deleterious, since it lowers the strength which the presence of mullite adds to the body.

In the same way that porosity greatly decreases the translucency of single-phase alumina, the presence of voids ($n_D = 1$) is deleterious in

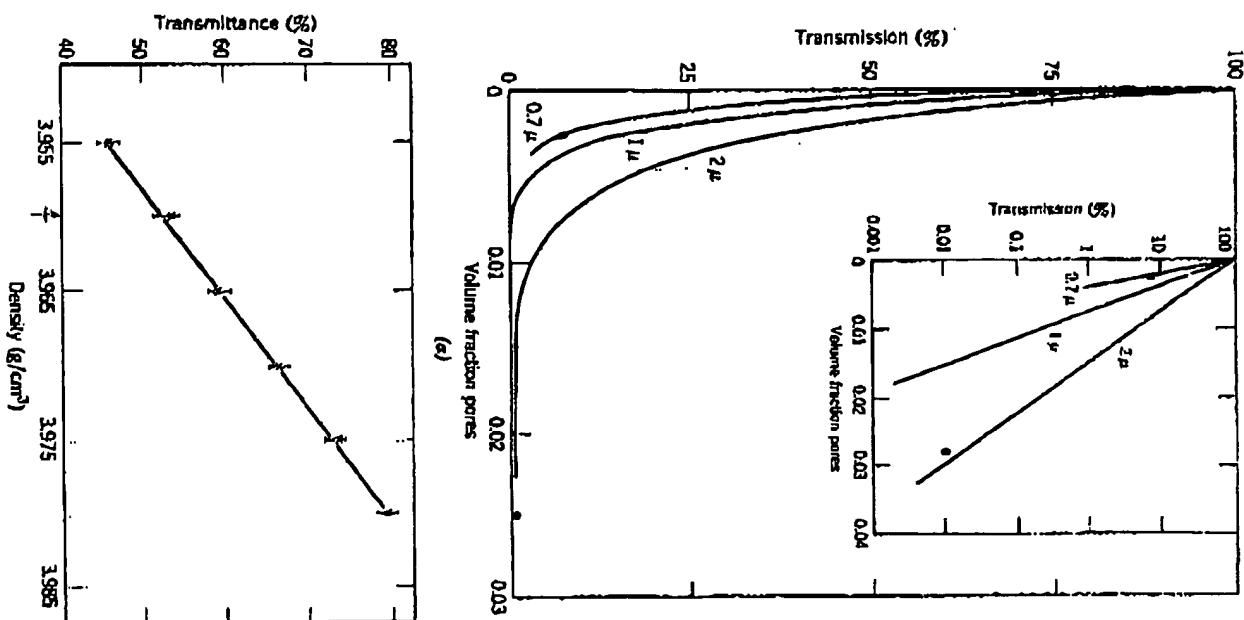


Fig. 13.18. (a) Transmission of polycrystalline alumina containing small amounts of residual porosity (equivalent thickness 0.5 mm). From D. W. Lee and W. D. Kingery, *J. Am. Ceram. Soc.*, 43, 594 (1960). (b) Effect of density on transmittance at 4.5 microns of Al_2O_3 , grain size 27 ± 3 microns, thickness 0.5 mm, surface finish $< 5 \mu$ in. From H. Grima et al., *Bull. Am. Ceram. Soc.*, 50, 962 (1971).